

04-29 11:22:53:41

## Sizing of Paper and Board


Dr. Boris Zhmud, Sveacon Consulting  
(boris.zhmud@sveacon.se)

www.sveacon.se


### Chemistry of the Wood Fibre

- Carbohydrates
- Lignin (20-30 wt.%)

- Cellulose (40-45 wt.%)
- Hemicelluloses (20-30 wt.%)



Cellulose




Hemicellulose

Carbohydrates:  $C_n(H_2O)_m$

www.sveacon.se


### Carbohydrates Are Quite Hydrophilic

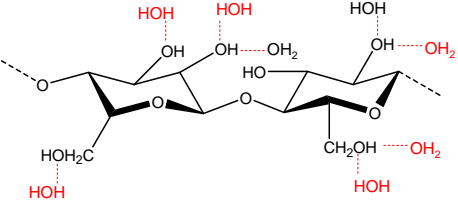


Heat of formation is 2 - 4 kcal per 1 mole of bonded water

www.sveacon.se

### ... and so is Paper




Water absorption is very fast



www.sveacon.se

### Contact Angle and Surface Energy

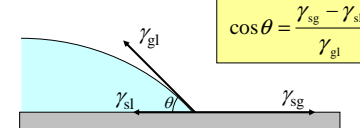

$$\cos \theta = \frac{\gamma_{sg} - \gamma_{sl}}{\gamma_{gl}}$$

Experiments show that, for sized paper, the contact angle with water is zero.

that's because one says that unsized paper has high surface energy

high


72 mJ/m<sup>2</sup>


unknown  $\gamma_{sg} - \gamma_{sl} \geq \gamma_{gl}$

likely quite negative due to hydration

www.sveacon.se

### The Idea of Sizing

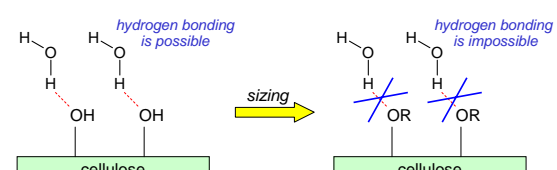

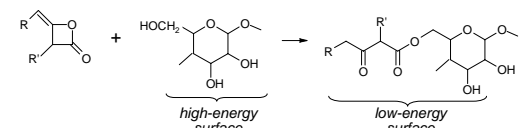

www.sveacon.se

### Once again, What's High, What's Low?

Experiments show that, for sized paper, the contact angle with water is over 90°.

that's because sized paper is said to have low surface energy

low  $\gamma_{sg} - \gamma_{sl} \ll \gamma_{gl}$   $72 \text{ mJ/m}^2$

unknown  $\gamma_{sg} - \gamma_{sl}$  a large positive value as there's no hydration

www.sveacon.se

### So, Sizing Reduces the Surface Energy

and the Oss-(not so)Good equation may be used to illustrate this,

$$\gamma_i (1 + \cos \theta_i) = 2[\alpha_i \gamma_{vdW} + \sqrt{\beta_i \gamma_{pol}}] \quad (i = 1, 2, \dots)$$

Wetting tests are done with water and ethylene glycol as test liquids.

Difficulties:

- > Surface roughness/porosity;
- > Extractives

www.sveacon.se

### Relation between Contact Angle and Surface Energy

Young-Dupré equation (energy-wise)

$$F = F_{lv} + F_{sl} + F_{sv}$$

$$F_{lv} = \gamma_{lv} S_{lv} = 2\pi R^2 \gamma_{lv} (1 - \cos \theta)$$

$$F_{sl} = \gamma_{sl} S_{sl} = \pi R^2 \gamma_{sl} \sin^2 \theta$$

$$F_{sv} = \gamma_{sv} S_{sv} = \text{const} - \pi R^2 \gamma_{sv} \sin^2 \theta$$

find the drop shape corresponding to a minimum of the excess free energy

$$\min_{\theta} F|_{V=\text{const}}$$

$$R(\theta) = \sqrt{\frac{3V}{\pi(2 - 3\cos\theta + \cos^3\theta)}}$$

$$\cos \theta = \frac{\gamma_{sv} - \gamma_{sl}}{\gamma_{lv}}$$

www.sveacon.se

### Thermodynamics of the Sizing Effect

A liquid drop will spontaneously spread over a surface as long as

$$dF = d\left(\sum_{ij} S_{ij} \gamma_{ij}\right) < 0$$

www.sveacon.se

### Relation between Contact Angle and Degree of Hydrophobization

Fully alkylated (paraffin) surface has a contact angle of about 110°

www.sveacon.se

### Capillarity and Wetting

www.sveacon.se

### Hydrophobic Plug and Cobb Test

**Cobb test**  
( $h = 100 \text{ cm}^3 / 100 \text{ cm}^2$ ):

$h \sim 1/r$

$pgh$

paper

www.sveacon.se

### Rosin Sizing

*Abietic acid*

*Pimaric acid*


COOH

COOH

COO<sup>-</sup> ... Al<sup>3+</sup> ... OH

- Rosin sizes are alkali metal salts of rosin (rosin is insoluble in water).
- Alum is essential for rosin bonding as rosin first reacts with aluminum ions and then aluminum rosinate is coordinately attached to an OH group of cellulose.
- The best sizing effect is achieved at pH 4.2 to 6.5.

www.sveacon.se

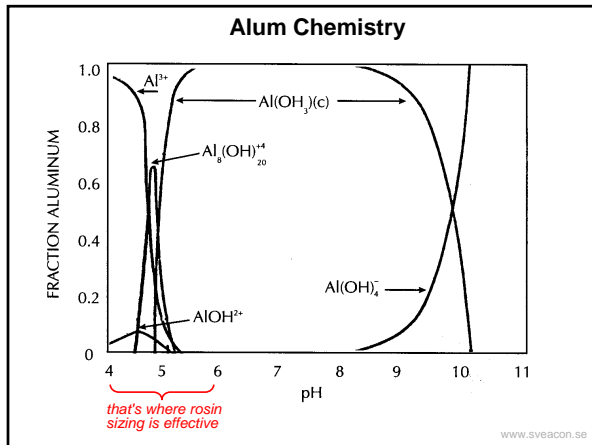

### Cellulose-Reactive Sizes

Water is more reactive than cellulose

**AKD sizing**

**ASA sizing**

www.sveacon.se

### Side Reactions

#### Size Hydrolysis

**AKD**

lactone

$\beta$ -keto acid

ketone

**ASA**

2,5-furandion ring

alkenyl succinic acid

Mechanism: nucleophilic attack ( $S_N2$ )

Kinetics: 2nd order (autocatalytic effect is possible)

www.sveacon.se







### Side Reactions






#### Size Oxidation

**ASA chain trimming**

**Rosin degradation**

www.sveacon.se

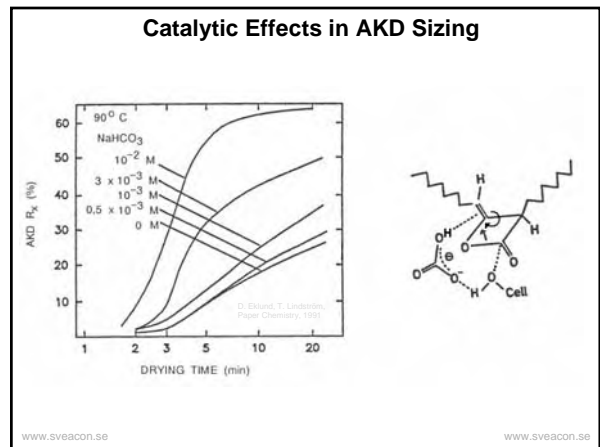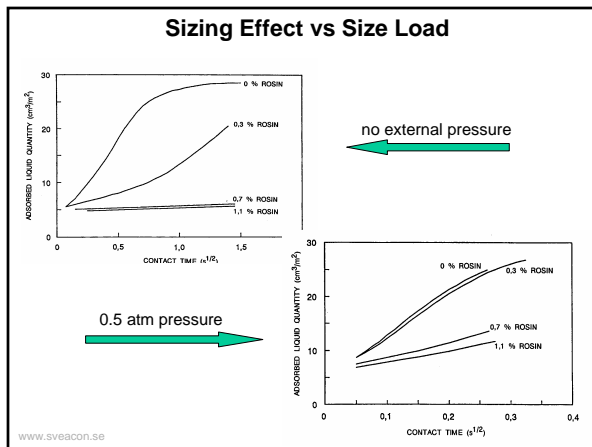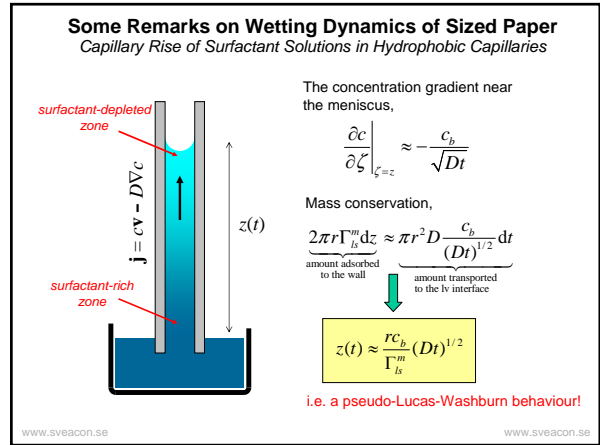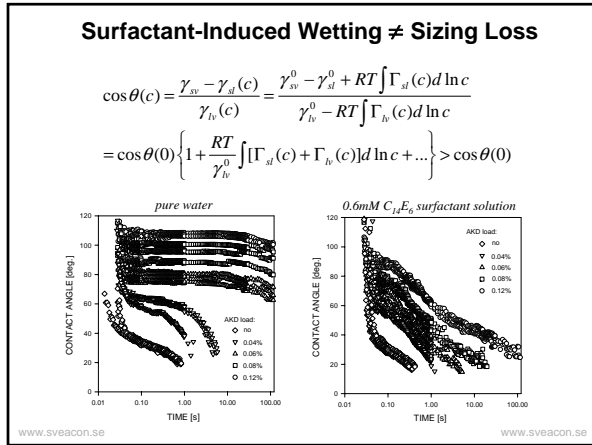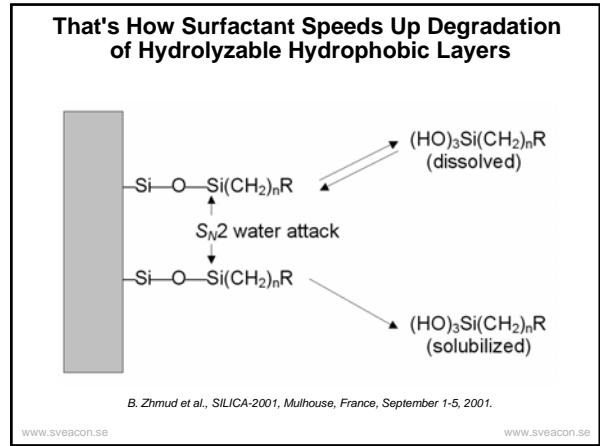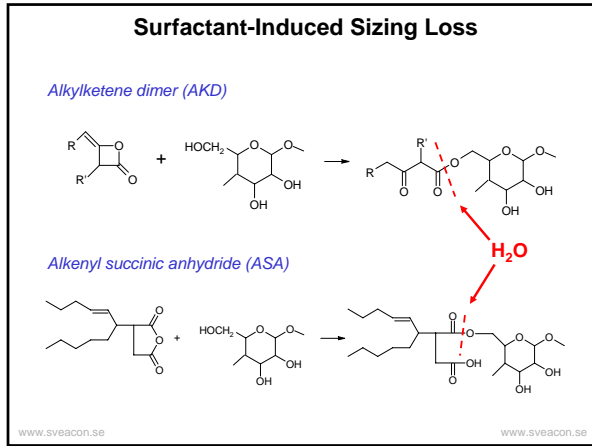

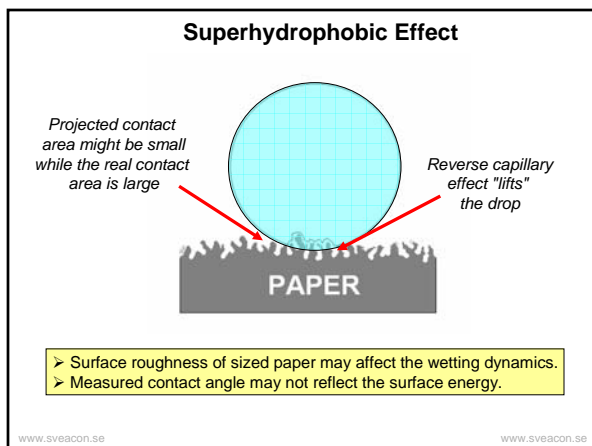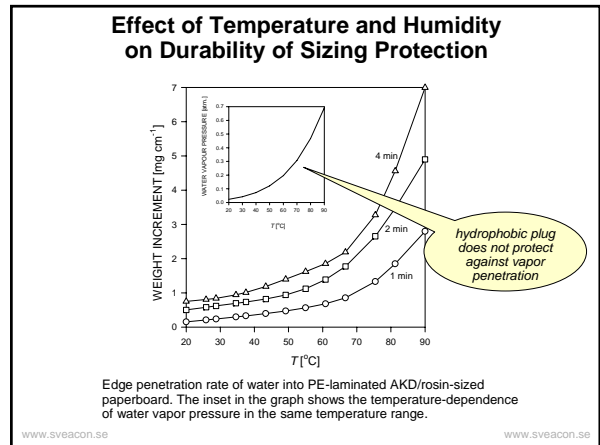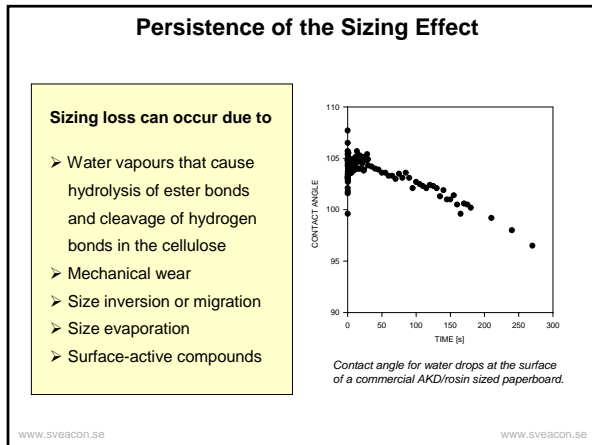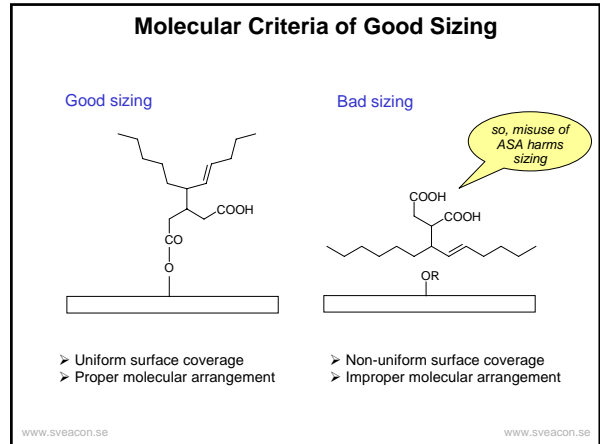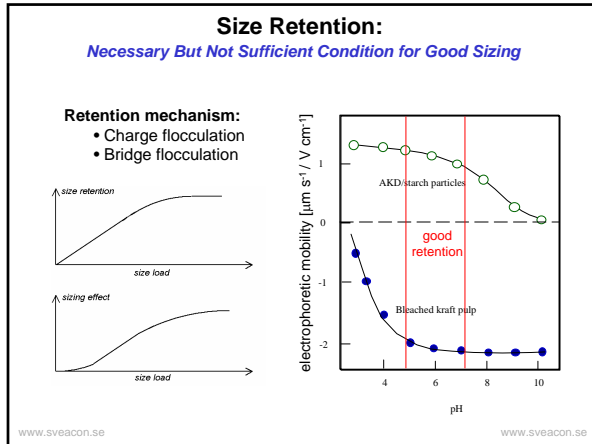

### Related Publications

1. J.C. Robert, Paper Chemistry, Blackie Academic, London, 1991.
2. W.F. Reynolds, The Sizing of Paper, Tappi, Atlanta, 1989.
3. D. Eklund, T. Lindström, Paper Chemistry, DT Paper Science Publ., Grankulla, 1991.
4. M. von Bahr, R. Seppänen, F. Tiberg, B. Zhmud, *J. Pulp Pap. Sci.* 30 (2004) 74.
5. R. Seppänen, M. von Bahr, F. Tiberg, B. Zhmud, *J. Pulp Pap. Sci.* 30 (2004) 70.
6. B. Zhmud, F. Tiberg, in *Surfactants in Polymers, Coatings, Inks and Adhesives*, (D.R. Karsa, Ed.) Blackwell Publ., CRC Press, 2003.
7. B. Zhmud, R. Seppänen, F. Tiberg, in *Scientific and Technical Advances in the Internal and Surface Sizing of Paper & Board*, Pira International conference proceedings, Prague, Dec. 2001.
8. R. Seppänen, F. Tiberg, M.-P. Valignat, *Nordic Pulp. Pap. Res. J.* 15, 452 (2000).
9. F. Tiberg, B. Zhmud, K. Hallstenson, M. von Bahr, *Phys. Chem. Chem. Phys.* 2 (2000) 5189.
10. B. Zhmud, F. Tiberg, K. Hallstenson, *J. Colloid. Interface Sci.* 228 (2000) 263.
11. M. von Bahr, F. Tiberg, B. Zhmud, B., *Langmuir* 12, 7069 (1999).
12. B. Zhmud, 27th IARIGAI, Research Conference on Advances in Paper and Board Performance (Graz, Austria, September 10-13, 2000).
13. B. Zhmud, Pira Int. Print. Conf. "Ink on Paper" (Brussels, Belgium, Jan. 14-16, 2003).
14. B. Zhmud, Int. Conf. on Functional Materials (Kiev, Ukraine, September 24-29, 2002).

www.sveacon.se